

## Spin Wave Theory of Double Exchange Magnets

D. I. Golosov

NORDITA, Blegdamsvej 17, DK-2100 Copenhagen Ø, Denmark

An isotropic half-metallic double exchange magnet with a direct superexchange coupling between the localized spins is studied within the spin-wave ( $1/S$ ) expansion. The momentum dependence of the spin wave spectrum (including quantum corrections) in the ferromagnetic phase at  $T = 0$  is investigated. Based on the calculated spin wave spectrum of the canted state, it is shown that as long as the external magnetic field is not too strong, the double exchange – superexchange competition does not result in a stabilization of a two-sublattice canted spin ordering.

The phenomenon of colossal magnetoresistance (CMR) continues to attract considerable attention to the properties of doped manganese oxides [1]. It is commonly accepted that the ferromagnetism observed in the CMR compounds in a wide range of doping values  $x$  is due to conduction electron-mediated double exchange interaction [2]; the latter in turn originates from a strong ferromagnetic Hund's rule exchange  $J_H$ , coupling the spins of itinerant electrons to the core spins of Mn ions. The present paper is devoted to an investigation of low-temperature spin dynamics of the double exchange magnets. Since the magnitude of localized spins is relatively large,  $S = 3/2$ , an appropriate theoretical framework is provided by the spin wave theory, which allows one to study the quantum-spin corrections within a controlled  $1/S$  expansion. Such an expansion for the case of double exchange ferromagnets was constructed in Ref. [3], to which the reader is also referred for a review of related theoretical and experimental work.

In the present paper, we treat an experimentally relevant case when an isotropic direct nearest-neighbour antiferromagnetic superexchange coupling,  $J$ , between the localized spins is present in addition to the double exchange interaction (see Ref. [4], and references therein). We consider the ferromagnetic phase first, analysing the momentum dependence of the magnon spectrum at  $T = 0$ , including quantum corrections. We then proceed to investigate the situation when the ferromagnetic state is destabilized as a consequence of double exchange – superexchange competition. We find that due to a spin-wave instability of de Gennes' two-sublattice canted state [2] in weak fields, this competition does not generally result in a canted spin ordering.

We write the Hamiltonian in the form

$$\mathcal{H} = -\frac{t}{2} \sum_{\langle i,j \rangle, \alpha} (c_{i\alpha}^\dagger c_{j\alpha} + c_{j\alpha}^\dagger c_{i\alpha}) - \frac{J_H}{2S} \sum_{i, \alpha, \beta} \vec{S}_i \vec{\sigma}^{\alpha\beta} c_{i\alpha}^\dagger c_{i\beta} + \frac{1}{S^2} J \sum_{\langle i,j \rangle} \vec{S}_i \vec{S}_j - \frac{1}{S} H \sum_i \left\{ S_i^z + \frac{1}{2} \sigma_{\alpha\beta}^z c_{i\alpha}^\dagger c_{i\beta} \right\}. \quad (1)$$

Here  $c_{j\alpha}$  are the electron annihilation operators,  $\vec{S}_i$  are

the operators of the core (localized) spins located at the sites of a square (or simple cubic) lattice, and the vector  $\vec{\sigma}^{\alpha\beta}$  is composed of Pauli matrices. The effects of magnetic field  $H$  on the orbital motion of conduction electrons are omitted. Throughout the paper we use units in which hopping  $t$ ,  $\hbar$ ,  $\mu_B$ , and the lattice spacing are all equal to unity, and we consider the  $T = 0$  case.

We begin with the case when the superexchange interaction is not too strong,  $J < J_c$  (see below), so that the ground state of the system at large  $S$  is ferromagnetic [5]. The carrier spectrum is then given by  $\epsilon_{\vec{k}}^{\uparrow, \downarrow} = \epsilon_{\vec{k}} \mp J_H/2 \mp H/(2S)$ , where  $\epsilon_{\vec{k}} = -\sum_{a=1}^d \cos k_a$  [6], and  $d$  is the dimensionality of the lattice. We will further assume that the value of Hund's rule coupling,  $J_H$ , is sufficiently large, resulting in a half-metallic situation with only spin-up electrons present in the ground state.

In the limit of  $J_H \rightarrow \infty$ , the leading-order term in the magnon spectrum acquires a Heisenberg-like form [7–9],

$$\omega_{\vec{p}}^{(0)} = (-2J + |E|/2d)(d + \epsilon_{\vec{p}})/S + H/S. \quad (2)$$

Here and below,  $E = \int_{-d}^{\epsilon_F} \epsilon \nu(\epsilon) d\epsilon$  is the total energy of a band with dispersion law  $\epsilon_{\vec{k}}$ , filled with  $x$  spinless fermions per site, whereas  $\nu(\epsilon)$  and  $\epsilon_F$  are the corresponding density of states and Fermi energy. The deviation from the cosine (Heisenberg-like) dispersion arises in the first quantum correction to the spin wave spectrum, which can be obtained along the lines of Ref. [3]:

$$\omega_{\vec{p}}^{(1)} = (xJ - |E|/4d)(d + \epsilon_{\vec{p}})/S^2 + \frac{1}{4S^2} \int (\epsilon_{\vec{q}} - \epsilon_{\vec{p}+\vec{q}}) n_{\vec{q}} \left\{ \int_{\epsilon_F}^d \frac{\xi - \epsilon_{\vec{p}+\vec{q}}}{\epsilon_{\vec{q}} - \xi} \nu(\xi) d\xi \right\} \frac{d^d q}{(2\pi)^d}. \quad (3)$$

Here  $n_{\vec{q}}$  is the Fermi distribution function for spin-up electrons.

At finite  $J_H$ , the spin-wave spectrum differs from that of a Heisenberg magnet already in leading order in  $1/S$  [7,9]:

$$\omega_{\vec{p}}^{(0)} = \frac{H - 2J(d + \epsilon_{\vec{p}})}{S} + \frac{J_H}{2S} \int \frac{\epsilon_{\vec{q}} - \epsilon_{\vec{p}+\vec{q}}}{\epsilon_{\vec{q}}^\uparrow - \epsilon_{\vec{p}+\vec{q}}^\downarrow} n_{\vec{q}} \frac{d^d q}{(2\pi)^d}. \quad (4)$$

The spin wave linewidth at  $T = 0$  originates from magnon-electron scattering processes: the oncoming magnon changes its energy and momentum while exciting an electron from under the Fermi surface. The leading-order term in magnon damping,  $\Gamma(\vec{p})$ , is proportional to  $S^{-3}$ . The expression for  $\Gamma(\vec{p})$  at finite  $J_H$  (and at  $J, H \geq 0$ ) can be obtained by multiplying the integrand in Eq. (10) of Ref. [3] by  $J_H^2/(\epsilon_{\vec{q}}^\dagger - \epsilon_{\vec{p}+\vec{q}}^\dagger)^2$ , and using our Eq. (4) for  $\omega_{\vec{p}}^{(0)}$ . As long as the system remains half-metallic, the behaviour of  $\Gamma(\vec{p})$  is similar to that in the  $J_H \rightarrow \infty$ ,  $J = 0$  case, studied in Ref. [3].

We will now consider the magnon spectrum in the  $J_H \rightarrow \infty$  case in more detail. At  $H = 0$ , the leading-order term in the deviation of the spectrum from a Heisenberg-like fit,  $\delta\omega_{\vec{p}} = \omega_{\vec{p}} - 2D(d + \epsilon_{\vec{p}})$  (where  $D$  is spin stiffness), originates from  $\omega_{\vec{p}}^{(1)}$ . The momentum dependence of the  $J$ -independent quantity  $\delta\omega_{\vec{p}}$  for various values of  $x$  in a 2D system is shown in Fig. 1. Taking also into account the decrease of  $D$  with decreasing  $x$  at  $J = 0$  (see Ref. [3]), we see a strong increase of relative magnitude of  $\delta\omega$  at small  $x$  [10]. We also find that at small  $x$ , the minimum of  $\delta\omega_{\vec{p}}$  is located at  $\vec{p} = \{\pi, \pi\}$ , rather than at  $\vec{p} = 0$  [11]. This agrees with the results of Refs. [12,13], and also follows from the expression

$$\delta\omega_{\vec{p}} = \frac{(d + \epsilon_{\vec{p}})^2}{4d^2 S^2} \int [\epsilon_{\vec{q}}^2 - (\partial\epsilon_{\vec{q}}/\partial\vec{q})^2] \left\{ \int_{\epsilon_F}^d \frac{\nu(\xi)d\xi}{\epsilon_{\vec{q}} - \xi} \right\} \frac{n_{\vec{q}} d^d q}{(2\pi)^d},$$

which is valid for the values of  $\vec{p}$  on the Brillouin zone (BZ) diagonal.

With increasing  $J$ , the ferromagnetic state becomes unstable at  $J = J_c$  as indicated by a softening of the spin wave spectrum,  $\omega_{\vec{p}}$ , at a certain value of momentum,  $\vec{p} = \vec{p}_0$  (either  $\omega_{\vec{p}} = 0$  at  $\vec{p} = \vec{p}_0 \neq 0$ , or  $D = 0$ ). At  $S \rightarrow \infty$ , the entire spectrum, Eq. (2), vanishes identically at  $J = J_{c0} = |E|/4d$  [14]. At finite  $S$ ,  $J_c = J_{c0} + \mathcal{O}(S^{-1})$  and  $\vec{p}_0$  may equal  $\{\pi, \pi\}$  only when the latter corresponds to the minimum of  $\delta\omega_{\vec{p}}$ . In the presence of a magnetic field  $H \gtrsim S^{-1}$ , the softening of the spin wave spectrum at  $J = J_{c0} + H/4d + \mathcal{O}(S^{-1})$  always occurs at  $\vec{p}_0 = \{\pi, \pi\}$ .

Softening of the spectrum at  $\vec{p} = \{\pi, \pi\}$  is consistent [12] with a transition into a de Gennes' canted phase [2], in which the momenta of the two ferromagnetic sublattices form an angle  $2\gamma$  with each other [15]. However, a definite conclusion about a transition into the canted state can not be made until the stability of this state is verified. As noted in Ref. [4] (Eqs. (B5) and (C4)), at  $1 \gg H \geq 0$  and at sufficiently small  $x$  the canted state is in fact unstable with respect to single-spin fluctuations. This statement has only variational significance, since it is likely that other, more complex distortions of canted spin arrangement can lower the energy of the system in a wider range of doping values. In order to study this situation in a systematic way, one has to turn to the spin wave spectrum of the canted state, which for  $J_H \rightarrow \infty$

and to leading order in  $1/S$  is given by a single branch,  $\Omega_{\vec{p}}$ , in a paramagnetic BZ:

$$\Omega_{\vec{p}}^2 = H(1 + \epsilon_{\vec{p}}/d)(\tan^2 \gamma)X_{\vec{p}}/(2S^2), \quad (5)$$

$$X_{\vec{p}} = (|E| + H)(1 - \epsilon_{\vec{p}}/d) + H(1 + \epsilon_{\vec{p}}/d)/(2\sin^2 \gamma) - H + \int \mathcal{P} \frac{\epsilon_{\vec{q}} + \epsilon_{\vec{p}+\vec{q}}}{\epsilon_{\vec{q}} - \epsilon_{\vec{p}+\vec{q}}} \epsilon_{\vec{q}} n_{\vec{q}} \frac{d^d q}{(2\pi)^d} \quad (6)$$

(see Appendix). Here,  $n_{\vec{q}}$  takes the same values as above, and the angle  $\gamma$  is given by  $4dJ \cos \gamma = H + |E|$ .

The expression (5) vanishes at  $H = 0$  as a consequence of the site-local continuous degeneracy of the canted state of a classical ( $S \rightarrow \infty$ ) double exchange – superexchange magnet [4]. This indicates a breakdown of the  $1/S$  expansion in the absence of a magnetic field. At  $H > 0$ , the degeneracy is lifted in favour of the canted state, which has the highest net magnetization among the continuously-degenerate (at  $H = 0$ ) states, and the validity of the  $1/S$  expansion is restored. By numerically evaluating the quantity  $X_{\vec{p}}$  for  $\vec{p}$  directed along the BZ diagonal and equal to the corresponding diameter of the Fermi surface, we found the canted state to be unstable ( $\Omega_{\vec{p}}^2 < 0$ ) in both 2D and 3D [16], provided that the magnetic field is small in comparison with the bandstructure energy scale,  $H \ll 1$ . This result holds for all values of  $x$ , with an exception of a narrow interval,  $|x - 0.5| \lesssim H^{1/2}$ , around the quarter-filling,  $x = 0.5$ . Thus, away from  $x = 0.5$ , the de Gennes' canted state is not a true classical ground state at  $H > 0$ . We believe that this is also the case at  $H = 0$ , especially given that the small- $x$  instability with respect to local fluctuations occurs at  $H = 0$  as well, while at some of the larger  $x$ , due to the softening of ferromagnetic spin-wave spectrum at  $\vec{p}_0 = 0$  the continuous ferromagnetic-to-canted transition at  $J = J_c$  is impossible.

Thus, the emerging situation at  $H = 0$  is that the energies of the entire manifold of classically degenerate states, which includes the canted state, do not correspond to the classical energy minimum [17]. We note the difference from a Kagomé antiferromagnet, which is an example of a local continuous degeneracy of a *true* classical ground state [18].

The local degeneracy of the canted state is also lifted at  $H = 0$  if one allows for a finite value of  $J_H \gg 1$ . In the ferromagnetic phase, the softening of the magnon spectrum, Eq. (4), at  $J = J_{c0} + \mathcal{O}(J_H^{-1})$  takes place away from  $\vec{p} = \{\pi, \pi\}$  for  $0.5 < x < 1$ , when  $\int [\epsilon_{\vec{k}}^2 - (\partial\epsilon_{\vec{k}}/\partial\vec{k})^2] n_{\vec{k}} d^d k < 0$ . A continuous transition to the canted state is then impossible. At  $x < 0.5$ , the spin wave spectrum in the canted state shows an instability of precisely the same kind as in the  $H > 0$ ,  $J_H \rightarrow \infty$  case [19].

The conclusion that the canted state is unstable at small  $H$  is in line with earlier theoretical results for  $T = 0$  [20], and with the fact that a checkerboard canted spin

arrangement has never been seen experimentally in the metallic phase of the CMR compounds. Thermal fluctuations, which were taken into account within a single-site mean field approach in Ref. [4], were also found to destabilize the canted spin ordering.

The author takes pleasure in thanking A. V. Chubukov, A. Luther, and J. Paaske for enlightening and motivating discussions.

## APPENDIX A:

The magnon spectrum in the canted state is obtained from the Hamiltonian (1) by performing the Holstein – Primakoff transformation with an appropriate rotation for each sublattice, followed by a canonical transformation (cf. Ref. [3]). After somewhat cumbersome calculation we find, to leading order in  $1/S$ ,  $S^2\Omega_{\vec{p}}^2 = A_{\vec{p}}^2 - B_{\vec{p}}^2$ , where

$$A_{\vec{p}} = J(1 + \cos 2\gamma)\epsilon_{\vec{p}} + H \cos \gamma - 2dJ \cos 2\gamma + J_H \times \quad (\text{A1})$$

$$\times \int \mathcal{P} \frac{J_H(\epsilon_{\vec{q}}^2 \cos 2\gamma - \epsilon_{\vec{p}+\vec{q}}^2) - 2\epsilon_{\vec{q}} \cos \gamma (\epsilon_{\vec{q}}^2 - \epsilon_{\vec{p}+\vec{q}}^2) \tilde{n}_{\vec{q}} d^d q}{4V_{\vec{q}}(V_{\vec{q}}^2 - V_{\vec{p}+\vec{q}}^2)} \frac{\tilde{n}_{\vec{q}} d^d q}{(2\pi)^d},$$

$$B_{\vec{p}} = J(1 - \cos 2\gamma)\epsilon_{\vec{p}} + \quad (\text{A2})$$

$$+ \frac{J_H^2 \sin^2 \gamma}{2} \int \mathcal{P} \frac{\epsilon_{\vec{p}+\vec{q}} \epsilon_{\vec{q}} \tilde{n}_{\vec{q}}}{V_{\vec{q}}(V_{\vec{q}}^2 - V_{\vec{p}+\vec{q}}^2)} \frac{d^d q}{(2\pi)^d}.$$

Here, the angle  $\gamma$  is found from the equation  $8dJ \cos \gamma = 2H - J_H \int \tilde{n}_{\vec{q}} \epsilon_{\vec{q}} V_{\vec{q}}^{-1} d^d q / (2\pi)^d$ , and the electron spectrum is given by  $\tilde{\epsilon}_{\vec{q}}^{\uparrow, \downarrow} = \mp V_{\vec{q}}$  with  $2V_{\vec{q}} = (J_H^2 - 4\epsilon_{\vec{q}} J_H \cos \gamma + 4\epsilon_{\vec{q}}^2)^{1/2}$ . In writing Eqs. (A1–A2) we again assumed that the chemical potential lies below the bottom of the upper band, whereas the Fermi distribution function in the lower band is denoted by  $\tilde{n}_{\vec{q}}$ .

The  $J_H \rightarrow \infty$  limit of Eqs. (A1–A2) yields Eqs. (5–6). It is interesting to note that in this limit, the value of  $\Omega_{\vec{p}}^2$  at  $p \ll k_F$  is proportional to  $p^2 H (|E| - \epsilon_F^2 \nu(\epsilon_F) + H)$ . Thus, at small  $H \ll 1$ , the requirement  $\Omega_{\vec{p}}^2 > 0$  for small  $p$  is identical with the thermodynamic stability condition for the canted phase (see Ref. [4], Eq. (C6)).

Finally, it is instructive to point out the connection between the spin-wave spectrum, Eqs. (5–6), and the small single-spin fluctuations studied in Ref. [4]. It turns out that the energies of such fluctuations [21] are proportional to the quantity

$$\int \frac{X_{\vec{p}} d^d p}{2(2\pi)^d} = |E| + \frac{H}{4 \sin^2 \gamma} + \int_{-d}^{\epsilon_F} \epsilon^2 \nu(\epsilon) \int_{-d}^d \mathcal{P} \frac{\nu(\xi) d\xi}{\epsilon - \xi} d\epsilon.$$

According to Eq. (5), at  $H > 0$  this quantity may be negative only when  $\Omega_{\vec{p}}$  is imaginary at some values of  $\vec{p}$ . This confirms that the instability with respect to small single spin fluctuations always leads to a spin-wave instability, as mentioned in the text.

- 
- [1] Physics of manganites, T.A. Kaplan and S. D. Mahanti, eds., (New York, Kluwer Academic/Plenum, 1999).
  - [2] P.-G. de Gennes, Phys. Rev. **118**, 141 (1960).
  - [3] D. I. Golosov, preprint cond-mat/9908202 [Phys. Rev. Lett., in press (2000)].
  - [4] D. I. Golosov, M. R. Norman, and K. Levin, Phys. Rev. **B58**, 8617 (1998).
  - [5] In fact, this is a well-justified assumption (cf. Ref. [3]).
  - [6] This form of  $\epsilon_{\vec{k}}$  (and hence, the tight-binding model used in Eq. (1)) is essential for the calculations reported here. We note that quantum fluctuations [3] renormalize the energies of spin-down electrons, which are therefore equal to  $\epsilon_{\vec{k}} + \mathcal{O}(S^{-1})$ .
  - [7] E. L. Nagaev, Zh. Eksp. Teor. Fiz. **56**, 1013 (1969) [Sov. Phys. JETP **29**, 545 (1969)]; Fiz. Tverd. Tela **11**, 2779 (1969) [Sov. Phys. Solid State **11**, 2249 (1970)].
  - [8] K. Kubo and N. Ohata, J. Phys. Soc. Jpn. **33**, 21 (1972).
  - [9] N. Furukawa, J. Phys. Soc. Jpn. **65**, 1174 (1996).
  - [10] T. A. Kaplan and S. D. Mahanti, J. Phys.: Condens. Matter, **9**, L291 (1997).
  - [11] Numerically, we find  $\delta\omega_{\{\pi, \pi\}} > \delta\omega_{\{0,0\}} = 0$  at  $0.31 < x < 0.93$ . In 3D,  $\delta\omega_{\{\pi, \pi, \pi\}} > 0$  at  $0.34 < x < 0.94$  [this is consistent with the variational results of P. Wirth and E. Müller-Hartmann, Eur. Phys. J. **B5**, 403 (1998), Fig. 3]. A more detailed investigation in 2D shows that at  $0.49 < x < 0.63$ , the minimum of  $\delta\omega_{\vec{p}}$  is located at  $\vec{p} = \{\pi, 0\}$ , rather than at  $\vec{p} = 0$ .
  - [12] E. L. Nagaev, Fiz. Tverd. Tela **14**, 773 (1972) [Sov. Phys. Solid State **14**, 658 (1972)].
  - [13] A. V. Chubukov and N. Shannon, unpublished (1999).
  - [14] The ferromagnetic state may become metastable already at  $J < J_{c0}$  (cf. Ref. [4], Fig. 6).
  - [15] At  $H > 0$ , spins of each sublattice form an angle  $\gamma$  with the  $z$  axis.
  - [16] This instability also persists in 1D, since the integral on the r. h. s. of Eq. (6) diverges at  $p = 2k_F$  and  $x \neq 0.5$ .
  - [17] This is expected to hold at all values of  $x$ , with a possible exception of  $x = 0.5$ .
  - [18] A. V. Chubukov, Phys. Rev. Lett. **69**, 832 (1992), and references therein.
  - [19] For the values of  $\vec{p}$  on the BZ diagonal, we find  $\Omega_{\vec{p}}^2 \propto J_H^{-1} S^{-2} (\partial \epsilon_{\vec{p}} / \partial \vec{p})^2 X_{\vec{p}} \int [\epsilon_{\vec{k}}^2 - (\partial \epsilon_{\vec{k}} / \partial \vec{k})^2] n_{\vec{k}} d^d k$  (where  $X_{\vec{p}}$  is given by Eq. (6) with  $H = 0$ ) to leading order in  $1/J_H$  and  $1/S$ .
  - [20] See, e.g., E. L. Nagaev, Usp. Fiz. Nauk **166**, 833 (1996) [Phys. Usp. **39**, 781 (1996)], and references therein; S. Yunoki and A. Moreo, Phys. Rev. **B58**, 6403 (1998); M. Yu. Kagan, D. I. Khomskii, and M. V. Mostovoy, Eur. Phys. J. **B12**, 217 (1999).
  - [21] See Ref. [4], Eq. (B5). We note a misprint on the r. h. s. of that equation, where the three integration limits should be changed from  $\pm 2$  to  $\pm 2t$  ( $t = \cos \gamma$ ). The value of the integral is then proportional to  $\cos \gamma$ .

FIG. 1. The momentum dependence of  $S^2\delta\omega_{\vec{p}}$  for a 2D system at  $H = 0$ . The solid, dashed, dotted and dashed-dotted lines correspond respectively to the band filling values  $x = 0.4$ ,  $x = 0.3$ ,  $x = 0.2$ , and  $x = 0.1$ .

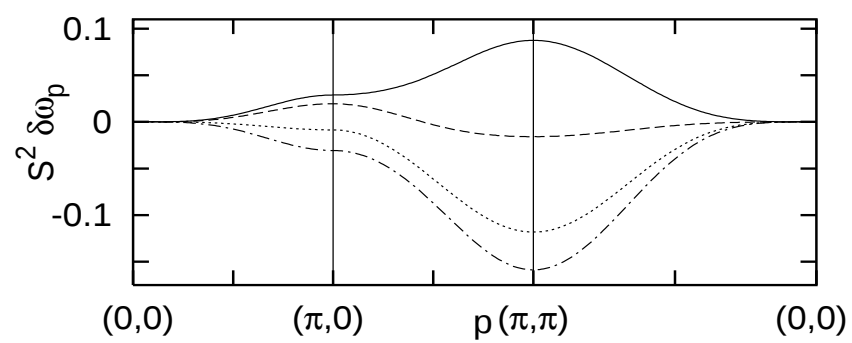


Fig. 1